



Received: 29-04-2026  
Accepted: 09-06-2026

ISSN: 2583-049X

## **Effect of Cutting Parameters on Cutting Temperature in C45 Steel Turning under Canola Oil-Based MQL**

**Trong-Hai Dinh**

Thai Nguyen University of Technology, Vietnam

Corresponding Author: **Trong-Hai Dinh**

### **Abstract**

Cutting temperature is one of the most critical factors affecting machining performance, tool life, and surface quality in turning operations. This study investigates the influence of cutting parameters on cutting temperature during the turning of C45 steel under canola oil-based minimum quantity lubrication (MQL) conditions. A Taguchi L9 orthogonal array was employed to evaluate the effects of cutting speed, feed rate, and depth of cut. Analysis of signal-to-noise (S/N) ratios and analysis of variance (ANOVA) were used to determine the significance of each machining

parameter and identify the optimal cutting conditions. The results revealed that cutting speed was the most influential factor, contributing approximately 76% to the variation in cutting temperature, followed by feed rate and depth of cut. The optimal parameter combination for minimizing cutting temperature was found to be a cutting speed of 120 m/min, a feed rate of 0.05 mm/rev, and a depth of cut of 0.5 mm. The findings demonstrate that canola oil-based MQL is an effective and sustainable cooling-lubrication strategy for reducing cutting temperature in the turning of C45 steel.

**Keywords:** C45 Steel, Turning, Cutting Temperature, Minimum Quantity Lubrication, Canola Oil, Taguchi Method

### **Introduction**

Manufacturing industries are increasingly required to improve machining efficiency while reducing environmental impacts and production costs<sup>[1, 2]</sup>. Conventional flood cooling has long been employed in machining operations to control friction and heat generation; however, the excessive use of cutting fluids creates environmental concerns, disposal challenges, and potential health risks for machine operators<sup>[3, 4, 5, 6]</sup>. Consequently, sustainable machining technologies have received significant attention from both researchers and industrial practitioners.

Among various sustainable lubrication techniques, Minimum Quantity Lubrication (MQL) has emerged as an effective alternative to conventional flood cooling<sup>[7, 8]</sup>. MQL delivers a small amount of lubricant directly into the cutting zone in the form of an aerosol, thereby reducing lubricant consumption while maintaining adequate cooling and lubrication performance<sup>[9, 10, 11, 12]</sup>. In addition, vegetable-based oils have become attractive candidates for MQL applications due to their biodegradability, renewability, and superior lubricating properties<sup>[13, 14, 15]</sup>. Canola oil, in particular, has demonstrated promising performance in metal cutting operations owing to its high lubricity and environmentally friendly characteristics<sup>[16]</sup>. C45 steel is widely used in the manufacture of shafts, gears, machine components, and structural parts because of its favorable combination of strength, toughness, and machinability<sup>[17, 18]</sup>. During the turning of C45 steel, a considerable amount of heat is generated as a result of plastic deformation and friction at the tool–chip interface. Excessive cutting temperature may accelerate tool wear, reduce machining accuracy, and negatively affect product quality<sup>[19, 20]</sup>. Therefore, controlling cutting temperature is essential for improving machining performance and ensuring process stability.

Previous studies have shown that cutting speed, feed rate, and depth of cut are the primary machining parameters influencing heat generation during turning operations. However, the combined effects of these parameters under canola oil-based MQL conditions have not been sufficiently investigated for C45 steel machining. Therefore, this study aims to evaluate the influence of cutting speed, feed rate, and depth of cut on cutting temperature during the turning of C45 steel under canola oil-based MQL. The Taguchi method and analysis of variance (ANOVA) are employed to identify the most significant factors and determine the optimal machining conditions for minimizing cutting temperature.

### **Experiment setup**

The experiments were conducted on C45 medium-carbon steel under minimum quantity lubrication (MQL) conditions using

canola oil as the lubricant. The turning operations were performed on an EMCO Maxturn 45 CNC lathe equipped with a carbide cutting tool. Cutting temperature was selected as the response variable and measured under different machining conditions. Three machining parameters, namely cutting speed ( $V_c$ ), feed rate ( $f$ ), and depth of cut ( $a_p$ ), were considered in this study. A Taguchi L9 orthogonal array was employed to design the experiments with three levels for each factor. The machining parameters and their levels are presented in Table 1, while the experimental results are summarized in Table 2.

**Table 1:** Machining Parameters and Their Levels

Level	$V_c$ (m/min)	$f$ (mm/rev)	$a_p$ (mm)
1	120	0.05	0.5
2	150	0.15	0.75
3	180	0.25	1

**Results and Discussion**

The experimental design and the corresponding cutting temperature values are presented in Table 2. The measured cutting temperature ranged from 71.2°C to 107.2°C under different machining conditions. The lowest temperature was obtained at a cutting speed of 120 m/min, a feed rate of 0.05 mm/rev, and a depth of cut of 0.5 mm, whereas the highest temperature was recorded at a cutting speed of 180 m/min, a feed rate of 0.25 mm/rev, and a depth of cut of 0.75 mm. In general, cutting temperature increased with increasing cutting speed and feed rate, indicating a higher rate of heat generation during the machining process.

**Table 2:** Experimental Design and Measured Cutting Temperature

Run	$V_c$	$f$	$a_p$	T
1	120	0.05	0.5	71.2
2	120	0.15	0.75	78.4
3	120	0.25	1	85.7
4	150	0.05	0.75	83.1
5	150	0.15	1	91.8
6	150	0.25	0.5	88.5
7	180	0.05	1	94.3
8	180	0.15	0.5	99.6
9	180	0.25	0.75	107.2

The response table for signal-to-noise (S/N) ratios is presented in Table 3. According to the smaller-is-better criterion, cutting speed exhibited the highest Delta value (2.15), followed by feed rate (1.09) and depth of cut (0.48). Therefore, the ranking of factor significance was  $V_c > f > a_p$ . Fig 1 further confirms this trend, showing a steep decline in S/N ratio with increasing cutting speed, while the influence of depth of cut was relatively small. The optimal parameter combination for minimizing cutting temperature was determined as  $V_c = 120$  m/min,  $f = 0.05$  mm/rev, and  $a_p = 0.5$  mm.

**Table 3:** Response Table for Signal-to-Noise Ratios (Smaller-is-Better)

Level	$V_c$	$f$	$a_p$
1	-37.87	-38.31	-38.65
2	-38.86	-39.04	-38.96
3	-40.02	-39.40	-39.14
Delta	2.15	1.09	0.48
Rank	1	2	3


The analysis of variance (ANOVA) results shown in Table 4 reveal that cutting speed was the most influential factor affecting cutting temperature, with an Adj-SS value of 726.73 and a contribution ratio of approximately 76.1%. Feed rate was the second most significant factor, contributing about 19.3%, whereas depth of cut had only a minor effect, contributing approximately 3.0%. The dominance of cutting speed can be attributed to the increased friction and plastic deformation occurring at higher cutting velocities, which leads to greater heat generation in the cutting zone. These findings are consistent with the commonly reported behavior of medium-carbon steel turning operations under MQL conditions.

**Table 4:** Analysis of Variance (ANOVA) for Cutting Temperature


Source	DF	Adj-SS	Adj-MS	F-Value	P-Value
$V_c$	2	726.73	363.363	48.06	0.020
$f$	2	184.43	92.213	12.20	0.076
$a_p$	2	28.25	14.123	1.87	0.349
Error	2	15.12	7.560		
Total	8	954.52			

**Table 5:** Statistical Performance of the Developed Model

S	R-sq	R-sq(adj)	R-sq(pred)
2.74955	98.42%	93.66%	67.92%

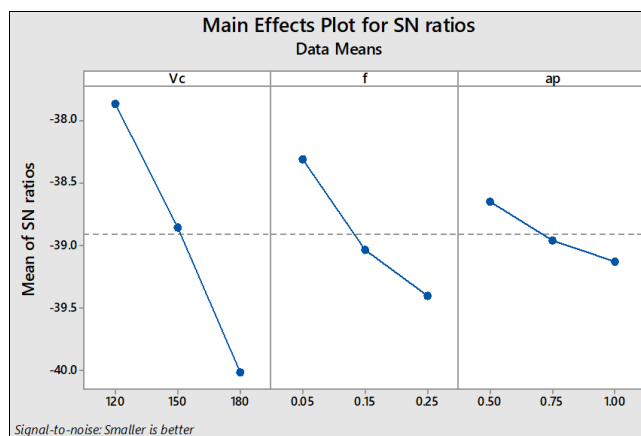

**Fig 1:** Main Effects Plot for S/N Ratios of Cutting Temperature

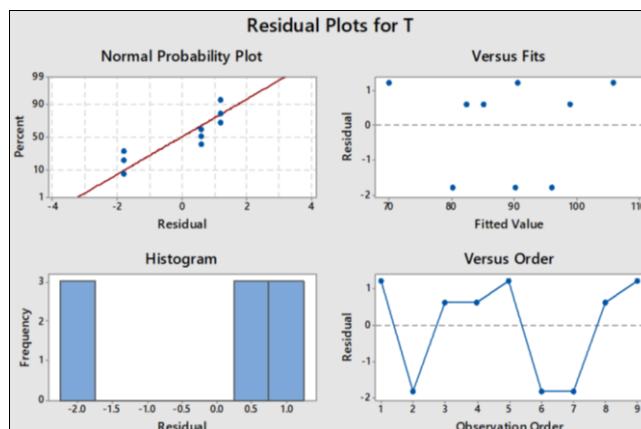

**Fig 2:** Residual Analysis of the Developed Model

The adequacy of the developed model was evaluated using statistical indicators and residual analysis. As shown in Table 5, the model achieved an  $R^2$  value of 98.42% and an adjusted  $R^2$  value of 93.66%, indicating excellent agreement

between the experimental and predicted results. The residual plots presented in Fig 2 show that the residuals are approximately normally distributed and randomly scattered around zero without any obvious pattern. This suggests that the developed model is statistically adequate and can reliably describe the relationship between machining parameters and cutting temperature within the investigated range.

### Conclusion

This study investigated the effects of cutting speed, feed rate, and depth of cut on cutting temperature during the turning of C45 steel under canola oil-based MQL conditions using the Taguchi method. The results demonstrated that cutting speed was the most influential factor, contributing approximately 76.1% to the variation in cutting temperature, followed by feed rate and depth of cut. The optimal machining parameters for minimizing cutting temperature were identified as a cutting speed of 120 m/min, a feed rate of 0.05 mm/rev, and a depth of cut of 0.5 mm. The developed model showed good agreement with the experimental results, with an  $R^2$  value of 98.42%. The findings confirm that canola oil-based MQL is an effective and environmentally friendly lubrication strategy for reducing cutting temperature in C45 steel turning operations.

### Acknowledgment

This research was conducted with the support of Thai Nguyen University of Technology.

### References

1. The-Vinh Do, Thanh-Dat Phan. An empirical investigation of SIO<sub>2</sub> nano concentration under MQL on surface roughness in hard milling of jis SKD61 steel. *Journal of Applied Engineering Science*. 2020; 18(3):432-437.
2. Aouici H, Bouchelaghem H, Yaltese MA, Elbah M, Fnides B. Machinability investigation in hard turning of AISI D3 cold work steel with ceramic tool using response surface methodology. *The International Journal of Advanced Manufacturing Technology*. 2014; 73:1775-1788.
3. Nguyen H-T, Hsu Q-C. Study on cutting forces and material removal rate in hard milling of SKD 61 alloy steel. *J. Chin. Soc. Mech. Eng.* 2017; 38(1):41-51.
4. Davim JP. *Machining of hard materials*. Springer Science & Business Media, 2011.
5. Do TV, Phan TD. Multi-objective optimization of surface roughness and MRR in milling of hardened SKD 11 steel under nanofluid MQL condition. *International Journal of Mechanical Engineering and Robotics Research*. 2021; 10:357-362.
6. Tran TH, *et al.* Improvement of wheel life by optimization of dressing parameters in surface grinding of SKD11 steel. In *Materials Science Forum*, Trans Tech Publ, 2021, 68-74.
7. Do T-V, Hsu Q-C. Optimization of minimum quantity lubricant conditions and cutting parameters in hard milling of AISI H13 steel. *Applied Sciences*. 2016; 6(3):83.
8. Dhar NR, Kamruzzaman M, Ahmed M. Effect of minimum quantity lubrication (MQL) on tool wear and surface roughness in turning AISI-4340 steel. *Journal of materials processing technology*. 2006; 172(2):299-304.
9. Phan T-D, Do T-V, Pham T-L, Duong H-L. Optimization of cutting parameters and nanoparticle concentration in hard milling for surface roughness of JIS SKD61 steel using linear regression and taguchi method. In *Advances in Engineering Research and Application: Proceedings of the International Conference on Engineering Research and Applications, ICERA 2020*, Springer, 2021, 628-635.
10. Astakhov VP. Metal cutting theory foundations of near-dry (MQL) machining. *IJMMM*. 2010; 7(1/2):1. Doi: 10.1504/IJMMM.2010.029843.
11. Do TV. Empirical model for surface roughness in hard milling of AISI H13 steel under nanofluid-MQL condition based on analysis of cutting parameters. *Journal of Mechanical Engineering Research and Developments*. 2020; 43(2):89-94.
12. Thi MHP, Nguyen QM, Nguyen AT, Nguyen VT, Vu MH, Do TV. A Hybrid RSM-PSO Approach for Enhancing Machining Performance in Nanofluid-Assisted Hard Turning. *Mathematical Modelling of Engineering Problems*, August 2025; 12(8):2681. Doi: 10.18280/mmep.120809.
13. He T, *et al.* Progress and trend of minimum quantity lubrication (MQL): A comprehensive review. *Journal of Cleaner Production*. 2023; 386:135809.
14. Boubekri N, Shaikh V. Minimum quantity lubrication (MQL) in machining: Benefits and drawbacks. *J Ind Intell Inf*. 2015; 3(3). Accessed: Mar. 19, 2025. [Online]. Available: <https://www.academia.edu/download/81201941/d97f17b193ee5ead8846aedf3e8ef633d25a.pdf>
15. Vu MH, Hue PTM, Huynh NT, Nguyen QM. Multi-objective Optimization for Enhanced Material Removal Rate and Reduced Machining Roughness in Hard Turning of SKD61 Alloy Steel. *Mathematical Modelling of Engineering Problems*. 2024; 11(3).
16. Belluco W, De Chiffre L. Testing of vegetable-based cutting fluids by hole making operations. *Tribology & Lubrication Technology*. 2001; 57(1):12.
17. Michalik P, Zajac J, Hatala M, Mital D, Fecova V. Monitoring surface roughness of thin-walled components from steel C45 machining down and up milling. *Measurement*. 2014; 58:416-428.
18. SreeramaReddy TV, Sornakumar T, VenkataramaReddy M, Venkatram R. Machinability of C45 steel with deep cryogenic treated tungsten carbide cutting tool inserts. *International Journal of Refractory Metals and Hard Materials*. 2009; 27(1):181-185.
19. Bacci da Silva M, Wallbank J. Cutting temperature: Prediction and measurement methods—a review. *Journal of Materials Processing Technology*, April 1999; 88(1):195-202. Doi: 10.1016/S0924-0136(98)00395-1.
20. Chu N-H, Nguyen V-D, Do T-V. Ultrasonic-assisted cutting: A beneficial application for temperature, torque reduction, and cutting ability improvement in deep drilling of Al-6061. *Applied Sciences*. 2018; 8(10):1708.